

# AISI D2 DATA SHEET

AISI D2 is a high-carbon, high-chromium tool steel alloyed with molybdenum and vanadium.

|                    |                              |     |     |      |     |     |
|--------------------|------------------------------|-----|-----|------|-----|-----|
| Typical analysis % | C                            | Si  | Mn  | Cr   | Mo  | V   |
|                    | 1.55                         | 0.3 | 0.4 | 11.8 | 0.8 | 0.8 |
| Delivery condition | Soft annealed approx. 210 HB |     |     |      |     |     |
| Color code         | Yellow/white                 |     |     |      |     |     |

## APPLICATIONS

AISI D2 is recommended for tools requiring very high wear resistance, combined with moderate toughness (shock-resistance). AISI D2 can be supplied in various finishes, including the hot-rolled, pre-machined and fine machined condition. It is also available in the form of hollow bar and rings.

## HEAT TREATMENT

### SOFT ANNEALING-

Protect the steel and heat through to 1560°F (850°C). Then cool in the furnace at 20°F (10°C) per hour to 1200°F (650°C), then freely in air.

### STRESS RELIEVING-

After rough machining, the tool should be heated through to 1200°F (650°C), holding time of 2 hours. Cool slowly to 930°F (500°C) then freely in air.

### HARDENING-

Preheating temperature: 1110-1290°F (600-700°C)  
Austenitizing temperature: 1810-1920°F (990-1050°C) but usually 1830°-1905°F (1000-1040°C).  
Protect the part against decarburization and oxidation during hardening.

### QUENCHING MEDIA-

- Oil (only very simple geometries)
- Vacuum (high speed gas)
- Forced air/gas
- Martempering bath or fluidized bed at 360-930°F (180-500°C), then cool in air


Note: Temper the tool as soon as its temperature reaches 120-160°F (50-70°C).

AISI D2 hardens through in all standard sizes.

## TEMPERING-

Choose the tempering temperature according to the hardness required by referencing the tempering graph. Temper twice with intermediate cooling to room temperature. Lowest tempering temperature at 360°F (180°C). Holding time at temperature for minimum 2 hours. High temperature tempers are the preferred process when dimensional stability is a concern, if tools are to be coated and/or if significant wire EDM will be performed in the hardened condition.

TEMPERING GRAPH

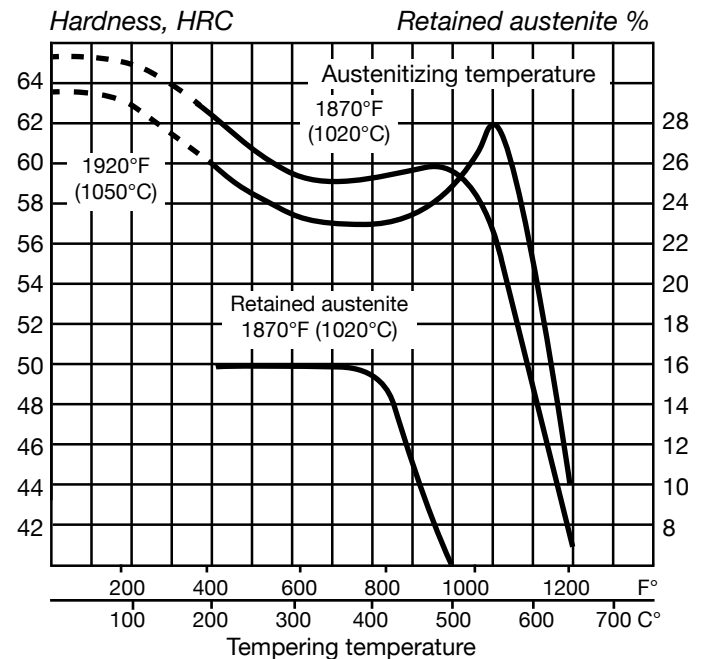

Note: The tempering graphs are valid for small samples. The hardness achieved is also dependent on the tool size.

### DIMENSIONAL CHANGES-

Dimensional change during hardening and tempering should not exceed 0.20% of the largest tool dimension, as long as the prescribed stress relief is performed.

# MACHINING

## MILLING-

### • Face and Square Shoulder Milling

| Cutting data parameters | Milling with carbide |              | Milling with HSS |
|-------------------------|----------------------|--------------|------------------|
|                         | Rough milling        | Fine milling | Fine milling     |
| Cutting speed ( $V_c$ ) |                      |              |                  |
| f.p.m.                  | 330-400              | 400-460      | 45               |
| m/min                   | 100-120              | 120-140      | 14               |
| Feed ( $f_z$ )          |                      |              |                  |
| inch/tooth              | 0.008-0.016          | 0.004-0.008  | 0.004            |
| mm/tooth                | 0.2-0.4              | 0.1-0.2      | 0.1              |
| Depth of cut ( $a_p$ )  |                      |              |                  |
| inch                    | 0.08-0.2             | -0.08        | -0.08            |
| mm                      | 2-5                  | -2           | -2               |
| Carbide designation     |                      |              |                  |
| US                      | C2                   | C2           | —                |
| ISO                     | K15*                 | K15*         | —                |

\*Use wear resistant  $Al_2O_3$  coated carbide grade, for example Sandvik Coromant GC 3015 or Seco T15M

### • End Milling

| Cutting data parameters | Type of milling           |                           |                           |
|-------------------------|---------------------------|---------------------------|---------------------------|
|                         | Solid carbide             | Carbide indexable insert  | High speed steel          |
| Cutting speed ( $V_c$ ) |                           |                           |                           |
| f.p.m.                  | 80                        | 260-430                   | 40 <sup>1)</sup>          |
| m/min                   | 25                        | 80-130                    | 12 <sup>1)</sup>          |
| Feed ( $f_z$ )          |                           |                           |                           |
| inch/tooth              | 0.001-0.008 <sup>2)</sup> | 0.003-0.008 <sup>2)</sup> | 0.002-0.014 <sup>2)</sup> |
| mm/tooth                | 0.03-0.20 <sup>2)</sup>   | 0.08-0.20 <sup>2)</sup>   | 0.05-0.35 <sup>2)</sup>   |
| Carbide designation     |                           |                           |                           |
| US                      | C2                        | C2                        | —                         |
| ISO                     | K20                       | K15 <sup>3)</sup>         | —                         |

1) For coated HSS end mill  $v_c \sim 80$  f.p.m./min. (24 m/min.)

2) Depending on radial depth of cut and cutter diameter.

3) Use a  $Al_2O_3$  coated carbide grade.

## DRILLING-

### • High Speed Steel Twist Drill

| Drill diameter |       | Cutting speed ( $V_c$ ) |       | Feed (f)    |           |
|----------------|-------|-------------------------|-------|-------------|-----------|
| inch           | mm    | f.p.m.                  | m/min | i.p.r.      | mm/r      |
| -3/16          | -5    | 30*                     | 10*   | 0.003-0.008 | 0.08-0.20 |
| 3/16-3/8       | 5-10  | 30*                     | 10*   | 0.008-0.012 | 0.20-0.30 |
| 3/8-5/8        | 10-15 | 30*                     | 10*   | 0.012-0.014 | 0.30-0.35 |
| 5/8-3/4        | 15-20 | 30*                     | 10*   | 0.014-0.016 | 0.35-0.40 |

1) For coated HSS drill  $v_c \sim 45$  f.p.m./min. (14 m/min.)

### • Carbide Drill

| Cutting data parameters | Type of drill            |                          |                              |
|-------------------------|--------------------------|--------------------------|------------------------------|
|                         | Indexable insert         | Solid carbide            | Brazed carbide <sup>1)</sup> |
| Cutting speed ( $V_c$ ) |                          |                          |                              |
| f.p.m.                  | 400-560                  | 115                      | 145                          |
| m/min                   | 120-170                  | 45                       | 35                           |
| Feed (f)                |                          |                          |                              |
| i.p.r.                  | 0.002-0.01 <sup>2)</sup> | 0.004-0.01 <sup>2)</sup> | 0.006-0.01 <sup>2)</sup>     |
| mm/r                    | 0.05-0.25 <sup>2)</sup>  | 0.10-0.25 <sup>2)</sup>  | 0.15-0.25 <sup>2)</sup>      |

1) Drill with internal cooling channels and brazed carbide tip.

2) Depending on drill diameter.

## ELECTRICAL DISCHARGE MACHINING EDM-

If EDM is performed in the hardened and tempered condition, the recast layer should be removed via stoning and/or polishing. If this is not possible, or for an additional safety factor, the tool should be given a subsequent stress temper at 50°F (28°C) below the lowest tempering temperature used during the heat treatment process. Equalize the temperature of the tool from surface to core and soak at the appropriate stress tempering temperature for 2 hours.

## GRINDING-

General grinding wheel recommendations for AISI D2 are given below.

### • Wheel Selection

| Type of grinding                 | Wheel recommendation |  |
|----------------------------------|----------------------|--|
|                                  | Soft Annealed Cond.  | Hardened Cond.   |
| Face grinding:<br>straight wheel | A46HV                | B151 R75 B3 <sup>1)</sup><br>3SG 46 HVS <sup>2)</sup><br>A46GV   |
| segments                         | A24GV                | 3SG 36 HVS <sup>2)</sup><br>A36GV                                |
| Cylindrical grind.               | A46LV                | B126 R75<br>A60IV<br>3SG 60 KVS <sup>2)</sup>                    |
| Internal grinding                | A46JV                | B126 R75 B3 <sup>1)</sup><br>3SG 60 JVS <sup>2)</sup><br>A60HV   |
| Profile grinding                 | A100LV               | B126 R100 B6 <sup>1)</sup><br>5SG 80 KVS <sup>2)</sup><br>A120JV |

1) If possible use CBN wheels for this application.

2) Grinding wheel from Norton Co.

## WELDING-

Good results when welding tool steel can be achieved if proper precautions are taken during welding (elevated working temperatures, joint preparation, choice of consumables and welding procedure). If the tool is to be polished or photo-etched, it is necessary to work with an electrode type of matching composition.

## FURTHER INFORMATION

### CANADIAN LOCATIONS-

Kitchener, Ontario +1 (519) 748-5317  
 Rexdale, Ontario +1 (905) 799-7474

### U.S. LOCATIONS-

Auburn, Massachusetts +1 (508) 757-3500  
 Blaine, Minnesota +1 (763) 585-9020  
 Cleveland, Ohio +1 (216) 362-8440  
 Meadville, Pennsylvania +1 (814) 337-6164  
 Chattanooga, Tennessee +1 (423) 790-7385